



UNIVERSITÀ POLITECNICA DELLE MARCHE
Repository ISTITUZIONALE

Investigating the “circular propensity” of road bio-binders: Effectiveness in hot recycling of reclaimed asphalt and recyclability potential

This is the peer reviewed version of the following article:

Original

Investigating the “circular propensity” of road bio-binders: Effectiveness in hot recycling of reclaimed asphalt and recyclability potential / Ingrassia, L. P.; Lu, X.; Ferrotti, G.; Conti, C.; Canestrari, F.. - In: JOURNAL OF CLEANER PRODUCTION. - ISSN 0959-6526. - ELETTRONICO. - 255:(2020).
[10.1016/j.jclepro.2020.120193]

Availability:

This version is available at: 11566/276996 since: 2024-04-29T13:27:45Z

Publisher:

Published

DOI:10.1016/j.jclepro.2020.120193

Terms of use:

The terms and conditions for the reuse of this version of the manuscript are specified in the publishing policy. The use of copyrighted works requires the consent of the rights' holder (author or publisher). Works made available under a Creative Commons license or a Publisher's custom-made license can be used according to the terms and conditions contained therein. See editor's website for further information and terms and conditions.

This item was downloaded from IRIS Università Politecnica delle Marche (<https://iris.univpm.it>). When citing, please refer to the published version.

(Article begins on next page)

Investigating the “circular propensity” of road bio-binders: effectiveness in hot recycling of reclaimed asphalt and recyclability potential

Lorenzo Paolo Ingrassia^{1*}, Xiaohu Lu², Gilda Ferrotti³, Carla Conti⁴ and Francesco Canestrari⁵

¹ PhD Student, Università Politecnica delle Marche, Department of Civil and Building Engineering, and Architecture (DICEA), Via Brece Bianche, 60131 Ancona, Italy, l.p.ingrassia@pm.univpm.it

² Senior Technical Specialist, Nynas AB, SE-14982 Nynäshamn, Sweden, xiaohu.lu@nynas.com

³ Assistant Professor, Università Politecnica delle Marche, Department of Civil and Building Engineering, and Architecture (DICEA), Via Brece Bianche, 60131 Ancona, Italy, g.ferrotti@staff.univpm.it

⁴ Scientist, Università Politecnica delle Marche, Department of Materials, Environmental Science and Urban Planning (SIMAU), Via Brece Bianche, 60131 Ancona, Italy, c.conti@staff.univpm.it

⁵ Full Professor, Università Politecnica delle Marche, Department of Civil and Building Engineering, and Architecture (DICEA), Via Brece Bianche, 60131 Ancona, Italy, f.canestrari@univpm.it

* Corresponding author, Tel.: +39 071 220 4780; fax: +39 071 220 4780.

E-mail address: l.p.ingrassia@pm.univpm.it

Abstract

In pavement engineering, the use of bio-binders and reclaimed asphalt (RA) promotes the principles of sustainability and circular economy, without penalizing or even improving the performance. In this regard, this study focuses on the “circular propensity” of bio-binders obtained by partially replacing a conventional bitumen with a bio-oil generated as a residue by the wood and paper industries. Specifically, the objectives are: 1) to assess the effectiveness of bio-binders in the hot recycling of traditional RA and 2) to evaluate, in a long-term perspective, their recyclability potential. For this purpose, two severely aged binders (one “RAP” binder recovered from reclaimed asphalt and one laboratory-produced “Bio-RAP” binder) and two fresh binders (one bio-binder and one bitumen) are blended to reproduce four hot recycled binders. The mechanical behaviour and the aging susceptibility of these blends are compared to those of a control virgin bitumen. The experimental investigation includes conventional tests, rheological testing and modelling (modified CAM model) as well as chemical analysis (Fourier transform infrared spectroscopy). The main results indicate that the hot recycling of reclaimed bio-asphalt (bio-RA) may lead to mixtures less susceptible to cracking as compared to the recycling of conventional RA, as well as the use of bio-binders in the hot recycling of conventional RA may be beneficial in terms of cracking. Even though the blends with the bio-binder are characterized by a lower aging rate, the permanent deformation behaviour of all the recycled blends studied is comparable in unaged and short-term aged conditions, i.e. the circumstances under which rutting is usually a concern. Finally, the recycled blends show significantly lower aging susceptibility than the control bitumen. Overall, these results suggest that the bio-binders studied are effective in the hot recycling of RA and 100% recyclable, and their use in asphalt pavements can lead to significant technical and environmental benefits.

Key Words: Pavement engineering; asphalt; bio-binders; recycling; sustainability; circular economy.

47 **1. Introduction**

48 The current environmental issues have highlighted the worldwide need for a cleaner production,
49 inspired by the principles of sustainability and circular economy. In fact, a sustainable and circular-
50 economy-based production would allow to meet the needs of the present without compromising the
51 ability of future generations to meet their own needs, by minimizing resources and energy
52 consumption, wastes and emissions (Brundtland, 1987; Geissdoerfer et al., 2017).

53 Generally speaking, the construction sector is responsible for significant environmental impact, as it
54 implies the consumption of natural resources (mostly non-renewable), causes emissions and
55 produces wastes (Ghisellini et al., 2018; Hendrickson and Horvath, 2000; Kucukvar and Tatari,
56 2013). Therefore, it is truly necessary for the sector to undergo important changes in a relatively
57 short time, such as the adoption of new construction technologies and innovative materials, aimed at
58 promoting sustainability and circular economy without penalizing the performance.

59 Within this framework, the use of bio-binders is attracting more and more interest in pavement
60 engineering (Ingrassia et al., 2019a). In general, bio-binders can be defined as binders in which
61 petroleum-based bitumen is partially replaced with renewable bio-oils, which typically derive from
62 residues or by-products like waste wood (Yang et al., 2014), non-edible vegetable biomass (Raouf
63 and Williams, 2010), waste cooking oil (Sun et al., 2016) or animal manure (Fini et al., 2011).
64 Previous studies have shown that, beside remarkable environmental benefits (Samieadel et al.,
65 2018a), the use of bio-oils as partial replacement of bitumen may also provide important technical
66 benefits such as reduced aging susceptibility (Hosseinneshad et al., 2019; Ingrassia et al., 2019b),
67 improved adhesion with aggregates (Bearsley and Haverkamp, 2007; Ingrassia et al., 2019c) and
68 increased moisture damage resistance (Bearsley and Haverkamp, 2007; Ingrassia et al., 2019c),
69 thanks to the bio-oils' chemical peculiarities.

70 At the same time, the progress in hot recycling technologies is allowing the production of new hot
71 asphalt mixtures containing extremely high percentages of reclaimed asphalt (RA) without
72 negatively affecting the performance (Zaumanis and Mallick, 2015; Zaumanis et al., 2014a, 2014b).
73 RA, which derives from the milling of asphalt pavements at the end of their service life, is a very
74 valuable material and, in hot recycling, the aged bitumen can be reactivated, at least partially (Lo
75 Presti et al., 2019). The reuse of RA promotes the principles of sustainability and circular economy,
76 by reducing the consumption of new non-renewable raw materials and the disposal of wastes,
77 exactly as in the case of bio-binders.

78 The combined use of bio-binders and RA, both composed of used/end-of-life materials, may
79 potentially result in sustainable asphalt mixtures with superior performance. Some bio-oils have
80 been already studied as possible rejuvenators for RA (Behnood, 2019; Cavalli et al., 2018; Gong et

al., 2016; Kowalski et al., 2017). However, to date, there are still uncertainties on the most suitable rejuvenator addition location in the asphalt plant, and some ad-hoc modification to the plant may also be necessary (Behnood, 2019; Lu et al., 2019; Zaumanis et al., 2019). A different employment for bio-oils in hot recycling might be to produce and store the bio-binder, by pre-blending bitumen and bio-oil. In this way, the issue of introducing the bio-based material in the production process could be easily overcome, provided that the stored bio-binder does not have problems in terms of storage stability, which is generally true (Abdullahi Ahmad et al., 2017; He et al., 2019; Ingrassia et al., 2019d), except in the presence of modifiers like polymers or crumb rubber.

At the same time, to ensure a wide market acceptance of bio-binders, it is essential – in a long-term perspective – to verify also if asphalt mixtures containing bio-binders can be 100% recycled at the end of their service life, as normally happens for traditional mixtures (Ingrassia et al., 2019a). Nevertheless, to date, no study has focused on the recyclability of bio-asphalt mixtures.

In this regard, this study has two main objectives: 1) to assess the effectiveness of bio-binders in the hot recycling of bitumen recovered from a typical RA, and 2) to evaluate, in a long-term perspective, the recyclability potential of bio-binders. For this purpose, two severely aged binders (one “RAP” binder recovered from reclaimed asphalt and one laboratory-produced “Bio-RAP” binder) and two fresh binders (one bio-binder and one bitumen) were blended to simulate four binders resulting from the hot recycling of asphalt. In order to investigate also their aging susceptibility, the blends were short-term and long-term aged in the laboratory. All binders were subjected to mechanical tests (including conventional tests as well as rheological testing and modelling) and chemical analysis (Fourier transform infrared spectroscopy).

102

103

104 **2. Materials and methods**

105

106 ***2.1 Base binders and control bitumen***

107 In order to reproduce in the laboratory the binder resulting from the hot recycling of asphalt, two severely aged binders were considered. The first one, coded as “RAP”, was recovered according to 108 EN 12697-3 (2018) from a typical reclaimed asphalt, taken from a milled pavement at the end of its 109 service life (more than 20 years). The second one, coded as “Bio-RAP”, was artificially aged in the 110 laboratory by subjecting the bio-binder A (described below) to one rolling thin film oven test 111 (RTFOT) (EN 12607-1, 2015) and two consecutive pressure aging vessel (PAV) conditionings (EN 112 14769, 2013) (i.e. 40 hours PAV). Indeed, according to several studies (Bowers et al., 2014; 113 Samieadel et al., 2018b; Zadshir et al., 2018), such procedure allows to prepare a reliable artificial 114

115 RA in the laboratory. This approach was necessary for producing RA deriving from a bio-binder
 116 (bio-RA), because no asphalt pavement containing bio-binders had been in service for a sufficiently
 117 long period of time when this study was carried out. It is worth noting that the RAP binder was
 118 harder, stiffer and more elastic than the Bio-RAP binder (Table 1 and Figure 1). These differences
 119 were properly considered in the materials preparation.

120 Moreover, the study included two different fresh binders to be combined with RAP and Bio-RAP: a
 121 bio-binder “A” composed of 10% by weight of a wood-based bio-oil, and a bitumen “B” having
 122 physical and mechanical properties similar to A (Table 1 and Figure 1), both characterized by a
 123 penetration of 120 dmm. As for the bio-oil used, it is a by-product of the wood and paper industries,
 124 and its physical and chemical properties can be found elsewhere (Ingrassia et al., 2019d).


125 In addition, a bitumen, coded as “Control” and having intermediate mechanical properties between
 126 the aged binders (RAP and Bio-RAP) and the fresh ones (A and B) (Table 1 and Figure 1), was
 127 added to the investigation as a commonly used virgin bitumen, with the aim of comparing its
 128 mechanical behaviour and aging susceptibility with those of the recycled blends.

129

130 Table 1 – Penetration and softening point of the base binders and the Control bitumen

Binder	Penetration [dmm]	Softening point [°C]
RAP	19	65.8
Bio-RAP	27	61.6
A	120	45.3
B	120	45.0
Control	55	52.4

131

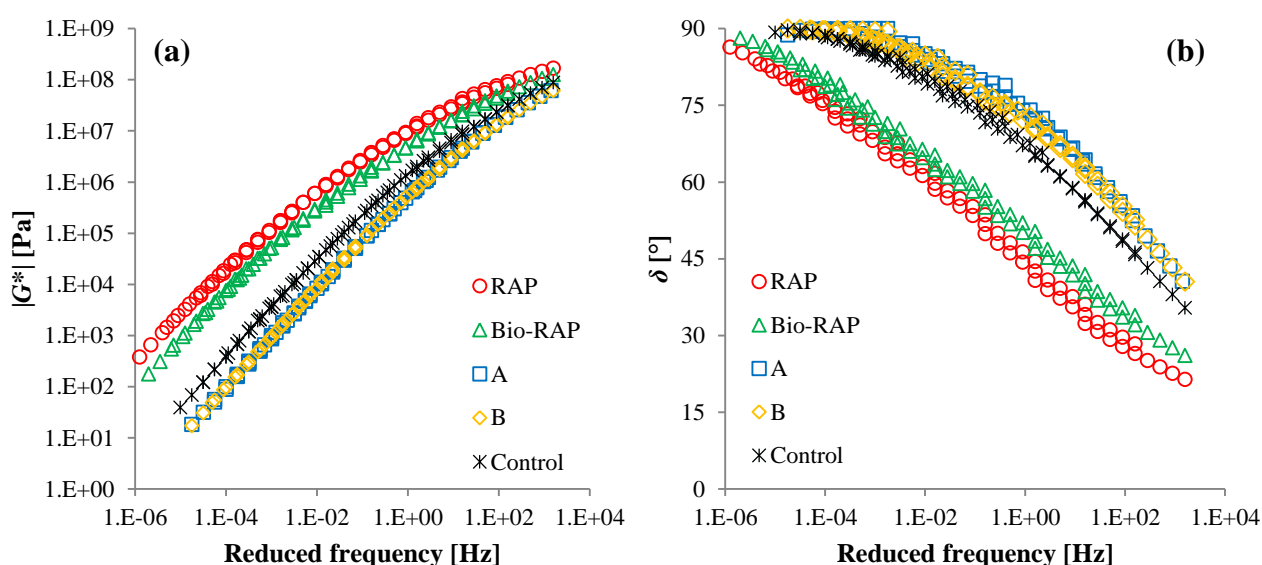

132

133 Figure 1 – Master curves of (a) complex modulus and (b) phase angle for the base binders and the Control
 134 bitumen, at a reference temperature of 20 °C

2.2 Recycled blends

The base binders (RAP, Bio-RAP, A and B) were combined according to appropriate proportions to prepare four blends (Table 2) having physical-mechanical properties similar to each other and comparable to the Control bitumen (see Section 3). After pre-heating the base binders at 160 °C (similarly to the temperatures usually adopted for hot recycling), the blends were produced by means of a laboratory mixer, considering a mixing speed of 500 rpm for 10 min.

A brief description of the recycled blends is provided in Table 2. Among the blends produced, B+RAP can be considered a sort of reference, as it represents the binder of a typical hot recycled asphalt mixture. The blend A+bio-RAP allows to evaluate, in a long-term perspective, the actual bio-binders' recyclability potential, whereas the blend A+RAP is useful to assess the effectiveness of bio-binders in hot recycling of bitumen. Finally, the blend B+bio-RAP represents an intermediate situation, opposite to that of A+RAP.

Table 2 – Recycled blends produced

Blend	Composition (by weight)	Description
A+RAP	71% A + 29% RAP	Recycled binder formed by a severely aged bitumen blended with a fresh bio-binder
B+RAP	71% B + 29% RAP	Recycled binder in which the aged and the fresh binders are composed of 100% bitumen
A+bio-RAP	62% A + 38% Bio-RAP	Recycled binder in which the aged and the fresh binders are bio-based (both contain 10% by weight of wood bio-oil)
B+bio-RAP	62% B + 38% Bio-RAP	Recycled binder formed by a severely aged bio-binder blended with a fresh bitumen

It is worth noting that the blends studied (Table 2) reproduce the binders of recycled asphalt mixtures with high reclaimed asphalt content. Indeed, the correspondence between the composition of the blends shown in Table 2 and the RA content in the recycled mixture can be evaluated through Equation (1) (Jiménez del Barco Carrión et al., 2017).

$$RA \text{ in the recycled mixture (\%)} = 100 \cdot \frac{RVB \cdot DB \text{ content}}{RAb \text{ content} \cdot DOB} \quad (1)$$

where *RVB* is the replaced virgin binder, i.e. the percentage of fresh binder in the recycled mixture that is replaced by the RA binder (29% for A+RAP and B+RAP and 38% for A+bio-RAP and B+bio-RAP); *DB content* is the designed binder content in the recycled mixture, given by fresh binder plus reactivated RA binder (fixed equal to a typical value of 5% in the calculation); *RAb content* is the binder content in the RA (fixed equal to a typical value of 4% in the calculation); *DOB* is the degree of blending between the RA binder and the fresh binder (assumed equal to 70%,

162 i.e. partial blending, according to Jiménez del Barco Carrión et al., 2017; Shirodkar et al., 2011;
163 Stimilli et al., 2015). Consequently, the blends A+RAP and B+RAP represent mixtures containing
164 about 50% RA by weight, while the blends A+bio-RAP and B+bio-RAP are representative of
165 mixtures containing about 70% RA by weight.

166 The four blends (Table 2) were short-term (RTFOT) and long-term (PAV) aged, in order to
167 reproduce the binder properties immediately after laying of hot recycled asphalt and after 10-15
168 year-service life of hot recycled asphalt, respectively.

169 Therefore, nineteen binders were studied overall, including the four base binders, the four blends at
170 three different aging levels as well as the Control bitumen at three aging levels.

171

172

173 **2.3 Mechanical tests**

174 The mechanical properties of the binders were investigated through conventional and rheological
175 tests.

176 The conventional properties, i.e. penetration and softening point, were assessed according to EN
177 1426 (2015) and EN 1427 (2015), respectively.

178 The rheological properties were studied through frequency sweep tests at different temperatures
179 with a dynamic shear rheometer (DSR) in plate-plate configuration using 8 mm and 25 mm
180 geometry, according to EN 14770 (2012). The norm of the complex modulus $|G^*|$ and the phase
181 angle δ were determined at temperatures ranging from 0 to 80 °C with a step of 10 °C, increasing
182 the frequency from 1 to 100 rad/s (i.e. from 0.159 to 15.9 Hz) with a fixed logarithmic step. All
183 tests were carried out at a low shear strain of 0.05%, in order to study the behaviour of the binders
184 in the linear viscoelastic (LVE) domain. At least two specimens were tested for each binder.

185 The master curves of $|G^*|$ and δ were developed by shifting the experimental data in the frequency
186 domain at 20 °C, which was chosen as reference temperature (T_{ref}). The temperature-dependency of
187 the shift factors was modelled according to the Williams-Landel-Ferry (WLF) law (Williams et al.,
188 1955), as in Equation (2).

189

$$\log a_T(T) = -\frac{C_1(T - T_{ref})}{C_2 + (T - T_{ref})} \quad (2)$$

190

191 where $a_T(T)$ is the shift factor at temperature T , while C_1 and C_2 are empirical constants.

192 The complex modulus master curve was then modelled through the modified Christensen-
 193 Anderson-Marasteanu (CAM) model (Bahia et al., 2001), defined as in Equation (3) in the case of
 194 bituminous binders.

195

$$|G^*(f)| = \frac{G_g}{\left[1 + \left(\frac{f_c}{f}\right)^k\right]^{\frac{m_e}{k}}} \quad (3)$$

196

197 where f is the reduced frequency, G_g is the glassy modulus (i.e. the value of the complex modulus
 198 for $f \rightarrow \infty$), f_c is the crossover frequency (i.e. the frequency at which the storage modulus G_1 and
 199 the loss modulus G_2 are approximately equal), k and m_e are dimensionless shape parameters. The
 200 distance between G_g and $|G^*(f_c)|$ is the so-called rheological index R , whose expression is as in
 201 Equation (4) in the case of bituminous binders.

202

$$R = \frac{m_e}{k} \log 2 \quad (4)$$

203

204 In the modelling procedure, G_g was fixed equal to 10^9 Pa based on literature suggestions (Anderson
 205 et al., 1994), whereas the parameters f_c , k and m_e (and consequently R) were determined by
 206 minimizing the error between model and experimental data, with the aim of achieving the best
 207 fitting.

208 In addition, the rheological behaviour at typical high service temperatures (60, 70 and 80 °C) was
 209 further investigated in terms of permanent deformation resistance through multiple stress creep and
 210 recovery (MSCR) tests, performed with the DSR with the 25 mm plate-plate geometry, according to
 211 EN 16659 (2015). At each testing temperature, two stress levels were considered, 0.1 and 3.2 kPa.
 212 The single stress level involved the application of 10 creep and recovery cycles, each one consisting
 213 in 1 s of loading and 9 s of recovery (without any load). The non-recoverable creep compliance J_{nr}
 214 and the percent strain recovery $\%R$ were determined for each binder, by testing at least two
 215 specimens.

216

217

218

219

220

221

222 **2.4 Chemical analysis**

223 The chemical characteristics of the binders were investigated through Fourier transform infrared
224 (FTIR) spectroscopy in transmission mode (Marsac et al., 2014). The specimens were prepared by
225 dissolving the binder in chloroform (CHCl_3). This solution was spread on sodium chloride (NaCl)
226 plates and then the solvent was evaporated, in order to have a very thin binder film to be analysed.
227 The transmittance/absorbance was evaluated at ambient temperature for wavenumbers between 500
228 and 4000 cm^{-1} with a resolution of 4 cm^{-1} , and each spectrum was obtained as the average of 16
229 consecutive scans on the specimen. For each binder, at least three specimens were tested and then
230 the average spectrum was determined. The spectral analysis was carried out with an integration
231 method consisting in the calculation of the areas under the most significant peaks by means of a
232 tangential approach (Hofko et al., 2017).

233

234

235 **3. Results and analyses**

236

237 **3.1 Conventional properties**

238 The penetration and the softening point data are summarized in Table 3. It can be observed that the
239 conventional properties of the four recycled blends are very similar at all aging levels. In terms of
240 penetration and softening point, the Control bitumen seems slightly harder than the recycled blends
241 in unaged conditions, but this difference tends to become smaller as aging increases. In general, the
242 results in Table 3 indicate that the recycled blends and the Control bitumen are characterized by
243 similar grade, which makes their comparison reasonable. The effect of aging emerges, as expected,
244 as a penetration decrease and softening point increase due to the binder hardening.

245 Nevertheless, it is worth noting that a more reliable comparison between the binders in terms of
246 mechanical behaviour as well as aging susceptibility can be made by considering the results of the
247 rheological and chemical tests, which are presented in the following Sections.

248

249

250

251

252

253

254

255

256 Table 3 – Penetration and softening point of the recycled blends and the Control bitumen

Aging level	Binder	Penetration [dmm]	Softening point [°C]
Unaged	A+RAP	64	50.1
	B+RAP	65	50.2
	A+bio-RAP	60	50.4
	B+bio-RAP	61	50.2
	Control	55	52.4
RTFOT	A+RAP	47	55.7
	B+RAP	43	54.8
	A+bio-RAP	45	54.7
	B+bio-RAP	47	55.4
	Control	35	55.7
PAV	A+RAP	25	61.6
	B+RAP	25	62.5
	A+bio-RAP	24	62.2
	B+bio-RAP	28	62.9
	Control	25	63.0

257

258

259 3.2 Master curves

260 Figures 2, 3 and 4 show the master curves of complex modulus $|G^*|$ and phase angle δ (experimental
261 data) for the recycled blends and the Control bitumen in unaged, short-term aged and long-term
262 aged conditions, respectively. In general, the rheological behaviour of the binders is comparable at
263 all aging levels. From the comparison between Figures 2, 3 and 4, it can be observed that for all
264 binders the effect of aging results in increased complex modulus and decreased phase angle,
265 meaning that the stiffness and the elasticity of the binders increase with aging (as expected). It is
266 also important to notice that the Control bitumen seems the binder that undergoes the most
267 significant rheological changes due to the aging process ($|G^*|$ increase and δ reduction). This finding
268 is in contrast with what emerged from the conventional tests, suggesting that the latter may not be
269 sufficiently reliable to examine the mechanical behaviour and aging susceptibility of bituminous
270 binders. It should be noted also that all binders are thermo-rheologically simple (including the ones
271 that contain the bio-oil), as perfectly continuous $|G^*|$ and δ master curves can be obtained by using
272 the same shift factors (Yusoff et al., 2011).

273

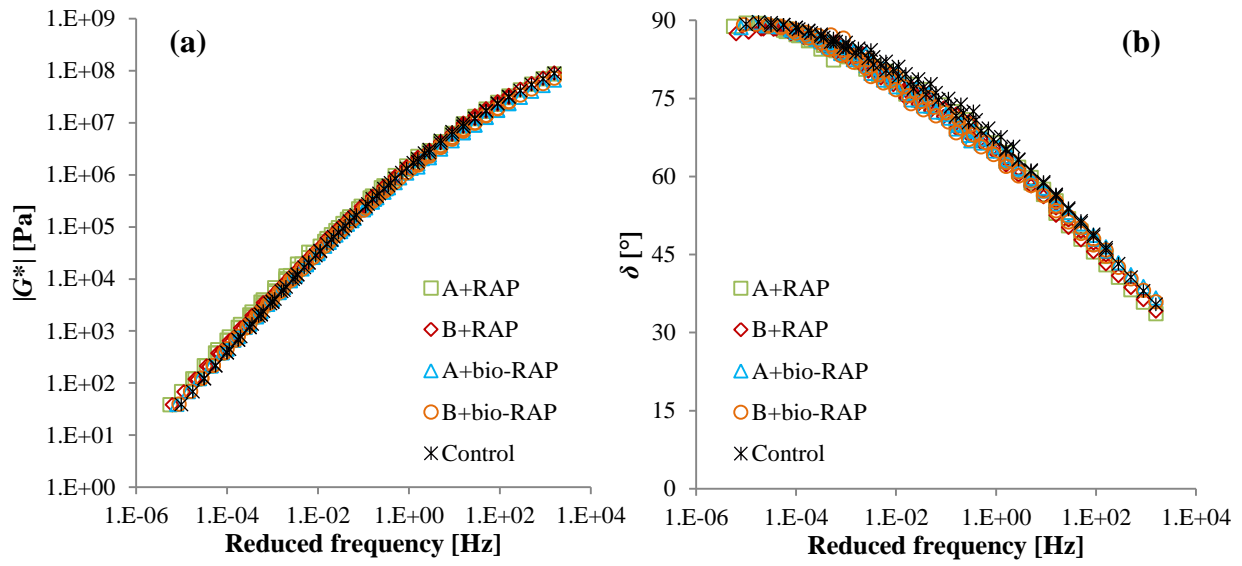


Figure 2 – Master curves of (a) complex modulus and (b) phase angle for the unaged recycled blends and Control bitumen, at a reference temperature of 20 °C

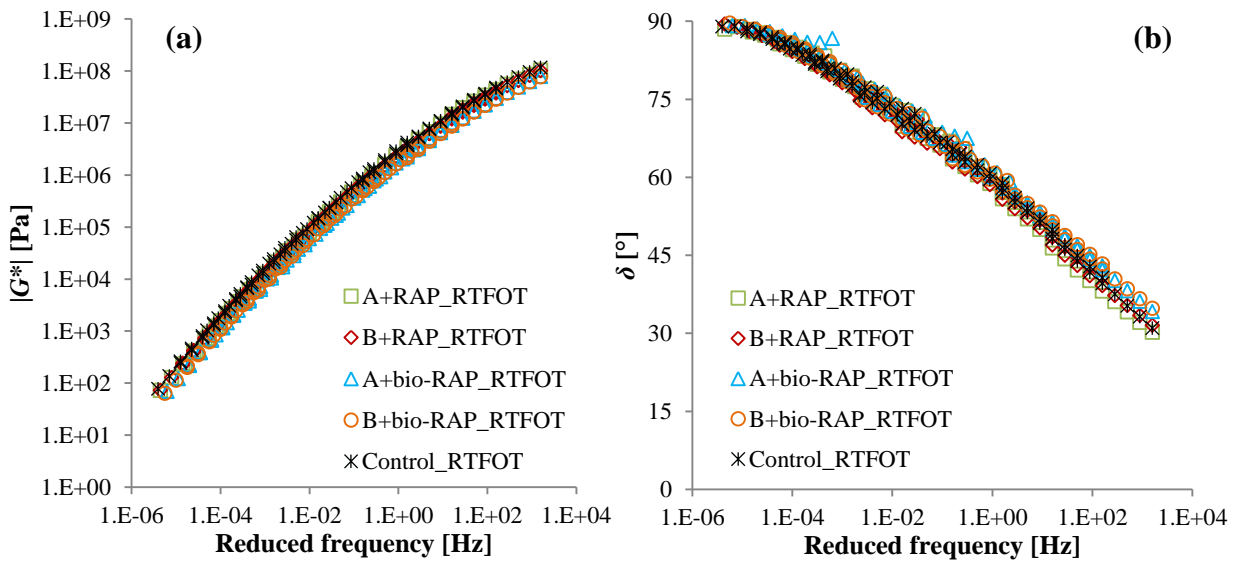


Figure 3 – Master curves of (a) complex modulus and (b) phase angle for the short-term aged recycled blends and Control bitumen, at a reference temperature of 20 °C

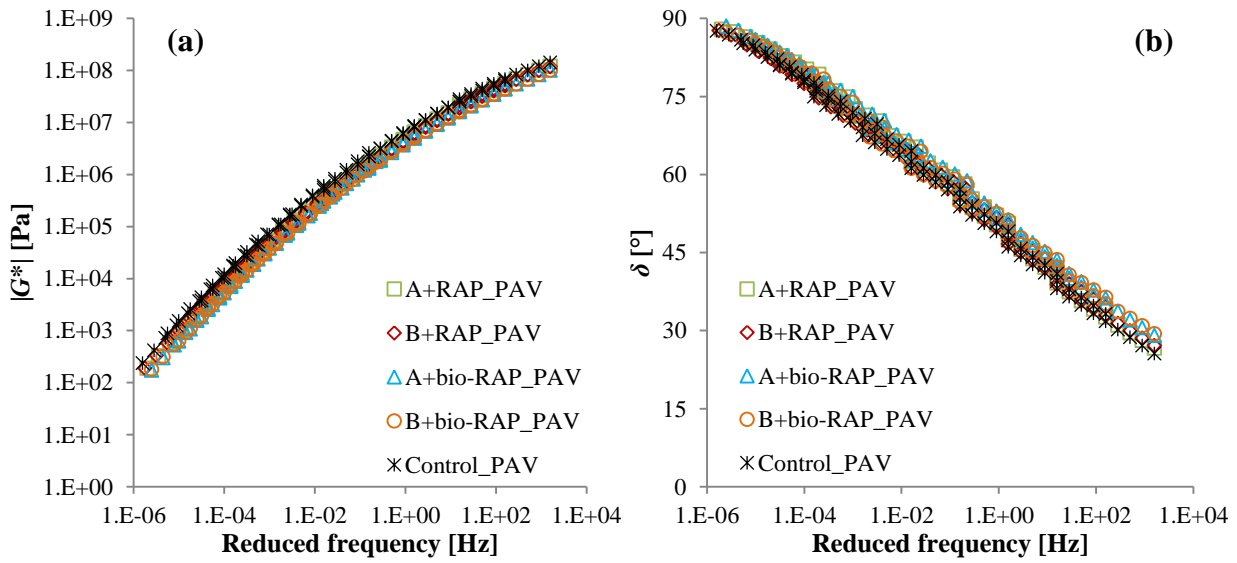


Figure 4 – Master curves of (a) complex modulus and (b) phase angle for the long-term aged recycled blends and Control bitumen, at a reference temperature of 20 °C

In order to better compare the rheological behaviour of the binders, the parameters deriving from the modelling of the complex modulus master curves can be considered. As an example of the model fitting to the experimental data, Figure 5 shows the $|G^*|$ master curve for A+bio-RAP at different aging levels (the other binders are not shown for brevity). The figure depicts more clearly the increase of $|G^*|$ due to aging.

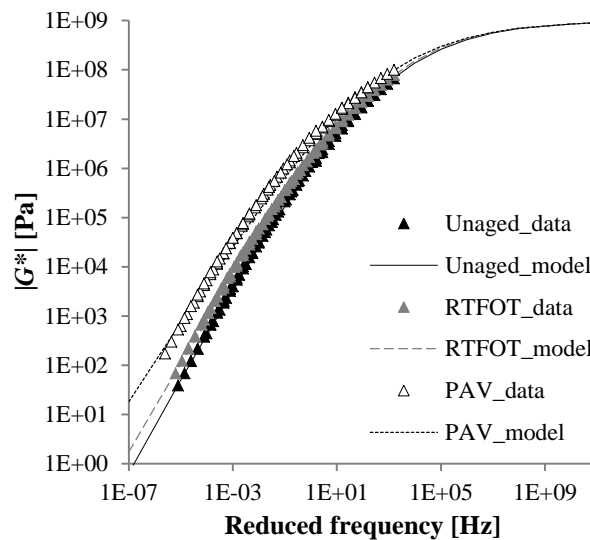


Figure 5 – Complex modulus master curve at 20 °C for A+bio-RAP at different aging levels (experimental data and modified CAM model)

296 Table 4 summarizes the modified CAM and WLF parameters obtained from the modelling. In terms
297 of modified CAM parameters, aging causes a general reduction of f_c (which does not emerge,
298 however, after RTFOT) and m_e as well as a slight decrease of k . Consequently, R decreases with
299 aging as well. Based on the physical meaning of these parameters (Bahia et al., 2001), the reduction
300 of the crossover frequency f_c indicates greater elastic component in the binder behaviour, while the
301 decrement of the rheological index R denotes a more rapid transition from the elastic to the viscous
302 behaviour (in fact, a hypothetical R value equal to zero would indicate a sudden transition between
303 perfectly elastic and purely viscous behaviour). As for the WLF parameters, greater C_1 and C_2
304 values are observed for higher aging levels, suggesting a reduced molecular mobility. All these
305 aging-related trends are in line with previous findings by Mazzoni et al. (2018), who studied the
306 influence of different rejuvenators on the aging of hot recycled asphalt binders. It is worth noting
307 that the variation of the parameters due to aging is more evident in the case of the Control bitumen,
308 denoting a possible greater aging susceptibility (in accordance with the observations made from the
309 comparison between Figures 2, 3 and 4), once again in contrast with the outcomes of the
310 conventional tests.

311 Since the RAP binder is stiffer and more elastic than the Bio-RAP binder (Figure 1), it exhibits
312 lower f_c , m_e and R as well as higher C_1 and C_2 than Bio-RAP. Conversely, the parameters are almost
313 the same for the bio-binder A and the conventional bitumen B, as their rheological behaviour is
314 practically identical (Figure 1). When the same aging level is considered, in general, all the recycled
315 blends and the Control bitumen exhibit comparable modified CAM and WLF parameters,
316 confirming the similarity of the master curves noticed from Figures 2, 3 and 4. More in detail, for
317 the blends containing Bio-RAP as aged binder, R tends to be higher, while C_1 and C_2 tend to be
318 lower, as compared to the other blends and the Control bitumen. Finally, f_c seems to be mainly
319 affected by the long-term aging rather than by the material type.

320

321

322

323

324

325

326

327

328

329

Table 4 – Modified CAM and WLF parameters

Binder	f_c [Hz]	k	m_e	R	C_1	C_2
RAP	200	0.21	0.75	1.08	39	382
Bio-RAP	300	0.21	0.79	1.14	31	307
A	400	0.22	1.06	1.48	16	181
B	400	0.21	1.06	1.51	15	171
A+RAP	350	0.22	0.95	1.33	22	228
A+RAP_RTFOT	350	0.21	0.89	1.28	24	248
A+RAP_PAV	250	0.20	0.80	1.20	32	323
B+RAP	350	0.22	0.95	1.30	21	220
B+RAP_RTFOT	350	0.21	0.89	1.25	24	248
B+RAP_PAV	250	0.20	0.80	1.20	35	348
A+bio-RAP	350	0.20	0.96	1.44	20	215
A+bio-RAP_RTFOT	350	0.20	0.92	1.38	22	239
A+bio-RAP_PAV	250	0.19	0.82	1.30	30	303
B+bio-RAP	350	0.21	0.96	1.41	19	206
B+bio-RAP_RTFOT	350	0.20	0.90	1.35	23	242
B+bio-RAP_PAV	250	0.19	0.82	1.30	30	303
Control	350	0.22	0.97	1.33	19	203
Control_RTFOT	350	0.21	0.89	1.20	25	257
Control_PAV	250	0.21	0.78	1.11	35	344

3.3 Fatigue parameter


In order to evaluate the fatigue behaviour of the binders, the rheological data were elaborated to determine the Superpave fatigue parameter $|G^*|\sin\delta$ introduced by the Strategic Highway Research Program (SHRP) (Kennedy et al., 1994). The parameter was calculated at the reference frequency of 10 rad/s (1.59 Hz) and at 20 °C, which was selected as a representative intermediate service temperature (Figure 6). In general, low values of $|G^*|\sin\delta$ indicate a good resistance of the binder to fatigue cracking, and a maximum value of 5000 kPa is set for $|G^*|\sin\delta$ after PAV aging.

From Figure 6a, it can be observed that the fresh binders A and B exhibit almost identical values of $|G^*|\sin\delta$, which are relatively low due to their high penetration grade (see Table 1). Moreover, as expected, the RAP binder shows a higher $|G^*|\sin\delta$ value as compared to the Bio-RAP binder.

As for the comparison between the recycled blends, Figure 6b shows that, at all aging levels, the blends containing Bio-RAP as aged binder are characterized by lower values of $|G^*|\sin\delta$ with respect to the blends containing RAP. Instead, the effect of the fresh binder type (A or B) is not very evident. Moreover, the Control bitumen exhibits higher $|G^*|\sin\delta$ values than the recycled blends, especially after aging, suggesting a possible faster aging rate (it is the only binder that does not meet the limit of 5000 kPa after PAV). These observations are generally in line with the results of rheological testing and modelling presented in Section 3.2.

350 The meaning of these results in terms of performance is discussed more in depth after the analysis
 351 of the aging susceptibility of the binders in Section 3.6.

352

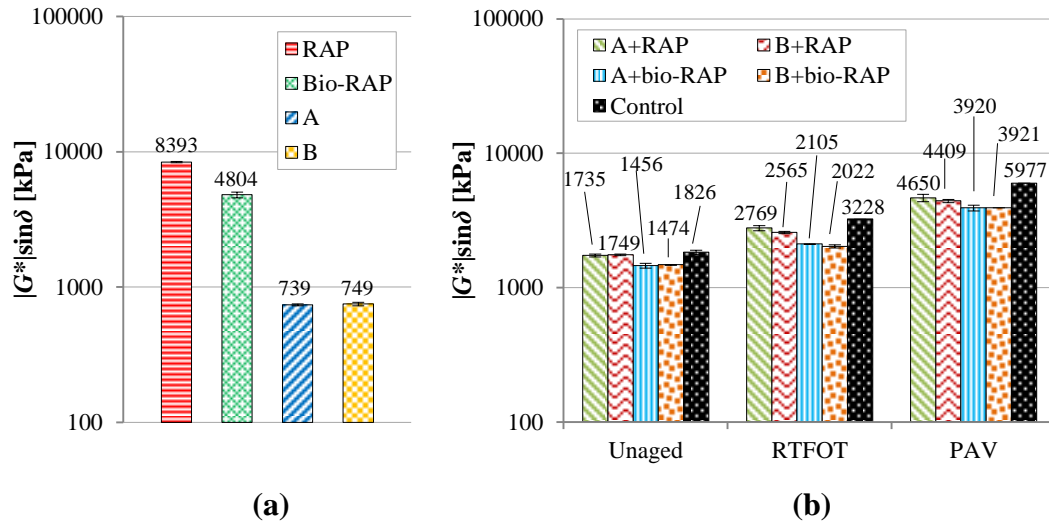

353

354 Figure 6 – Fatigue parameter at 20 °C and 10 rad/s for (a) base binders, (b) recycled blends and Control
 355 bitumen at different aging levels

356

357

358 3.4 Non-recoverable creep compliance and percent strain recovery


359 The values of the non-recoverable creep compliance (J_{nr}) obtained at 70 °C and 3.2 kPa are shown
 360 in Figure 7, whereas Figure 8 displays the values of the percent strain recovery ($\%R$) calculated at
 361 the same temperature and stress level.

362 Firstly, it can be noted that – as expected – aging causes a reduction of J_{nr} and a simultaneous
 363 increase of $\%R$. In fact, as already discussed in Section 3.2, the binder becomes stiffer and more
 364 elastic with aging, thus exhibiting lower deformability and higher recovery capability. In general,
 365 lower J_{nr} and higher $\%R$ indicate a greater resistance against permanent deformations.

366 As for the base binders (Figures 7a and 8a), the bio-binder A and the bitumen B are characterized
 367 by identical values of J_{nr} and $\%R$ (equal to zero), further confirming that their mechanical behaviour
 368 is very similar (Table 1 and Figure 1). Instead, the RAP binder exhibits lower J_{nr} and higher $\%R$ as
 369 compared to the Bio-RAP binder, in line with what observed in terms of conventional properties
 370 and master curves (Table 1 and Figure 1).

371 Figures 7b and 8b show that all the recycled blends and the Control bitumen have comparable J_{nr}
 372 and $\%R$ values in unaged conditions. Some differences between the binders emerge with aging,
 373 once more suggesting that the binders may have dissimilar aging susceptibility. Specifically, after
 374 aging, the blends containing Bio-RAP tend to exhibit the highest J_{nr} values together with the lowest

375 %*R*, while the Control bitumen, on the contrary, is characterized by the lowest *J_{nr}* values and the
 376 highest %*R*. The effect of the fresh binder type in the blend can be mainly observed in the percent
 377 strain recovery after PAV (Figure 8b). In fact, the blends containing A (A+RAP, A+bio-RAP)
 378 present smaller %*R* values than the corresponding blends containing B (B+RAP, B+bio-RAP). All
 379 these observations are consistent with the results presented in Sections 3.2 and 3.3.
 380 Analogous observations can be made at the other temperatures (60 and 80 °C) and stress levels (0.1
 381 kPa) investigated (not shown for brevity).
 382 The implications of these outcomes in terms of performance are further discussed in Section 3.6,
 383 after the in-depth analysis of the aging susceptibility of the binders.
 384

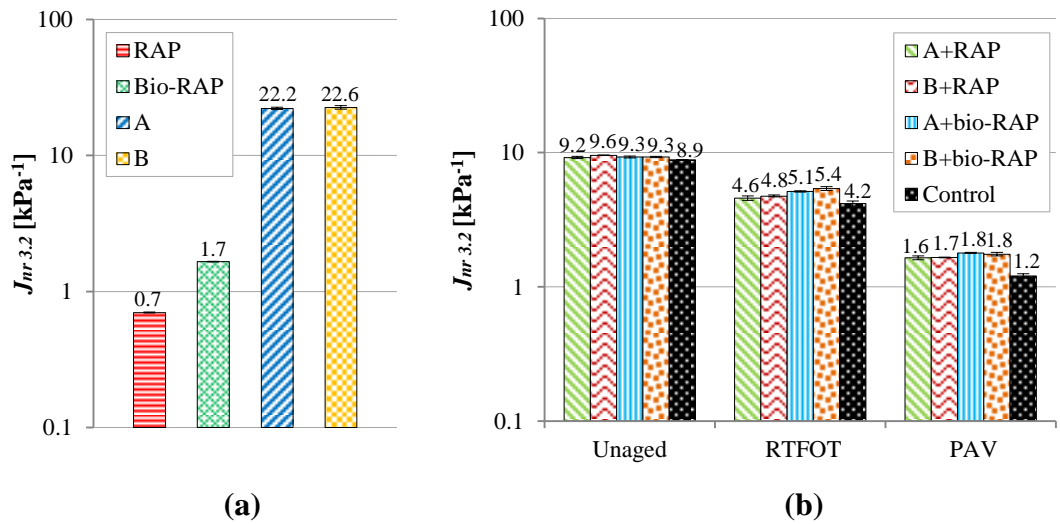

385
 386 Figure 7 – Non-recoverable creep compliance at 70 °C and 3.2 kPa for (a) base binders, (b) recycled blends
 387 and Control bitumen at different aging levels
 388
 389
 390

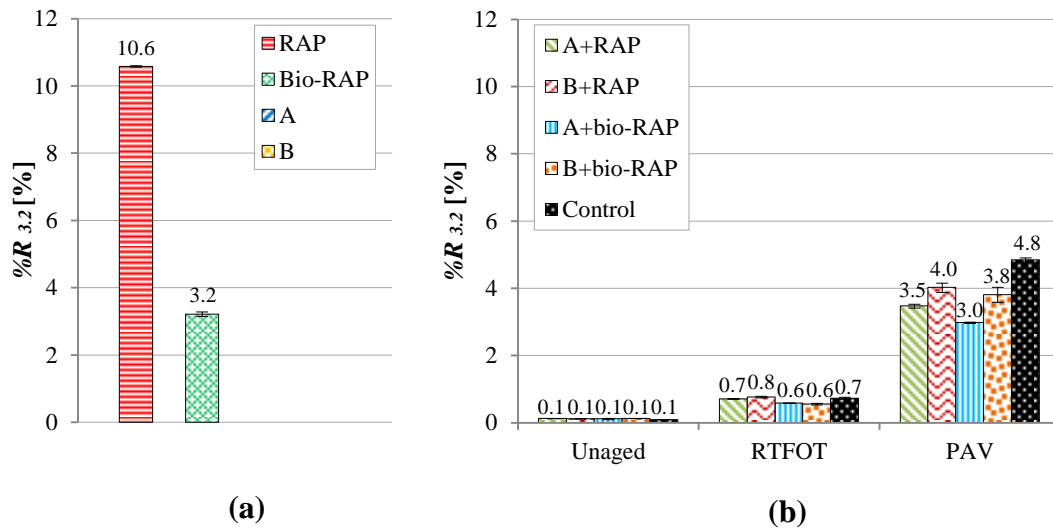


Figure 8 – Percent strain recovery at 70 °C and 3.2 kPa for (a) base binders, (b) recycled blends and Control bitumen at different aging levels

3.5 FTIR spectra

The absorbance spectra of the base binders are shown in Figure 9, where the main peaks are highlighted. From the spectra of binders A and Bio-RAP, it can be observed that the bio-oil modification is identified by the peak at 1735 cm^{-1} , which is absent in the spectrum of conventional bitumen (e.g. binders B and RAP) and corresponds to the C=O stretch of the bio-oil's esters, as already shown in previous studies (Ingrassia et al., 2019b, 2019d). Moreover, for all the binders, the effect of aging emerges as the formation of new bonds at about 1700 and 1030 cm^{-1} (see the comparison between bio-based binders A and Bio-RAP and between conventional bitumens B and RAP), corresponding respectively to the C=O stretch of carbonyl functional groups and the S=O stretch of sulfoxides. It is well known that the C=O and S=O bonds formed during aging at these wavenumbers are responsible for significant physical and rheological changes undergone by bituminous binders (Petersen, 2009; Petersen and Glaser, 2011). However, a previous study (Ingrassia et al., 2019b) highlighted that, for the same type of bio-binders, aging can imply also the formation of new compounds that show absorption at 1735 cm^{-1} .

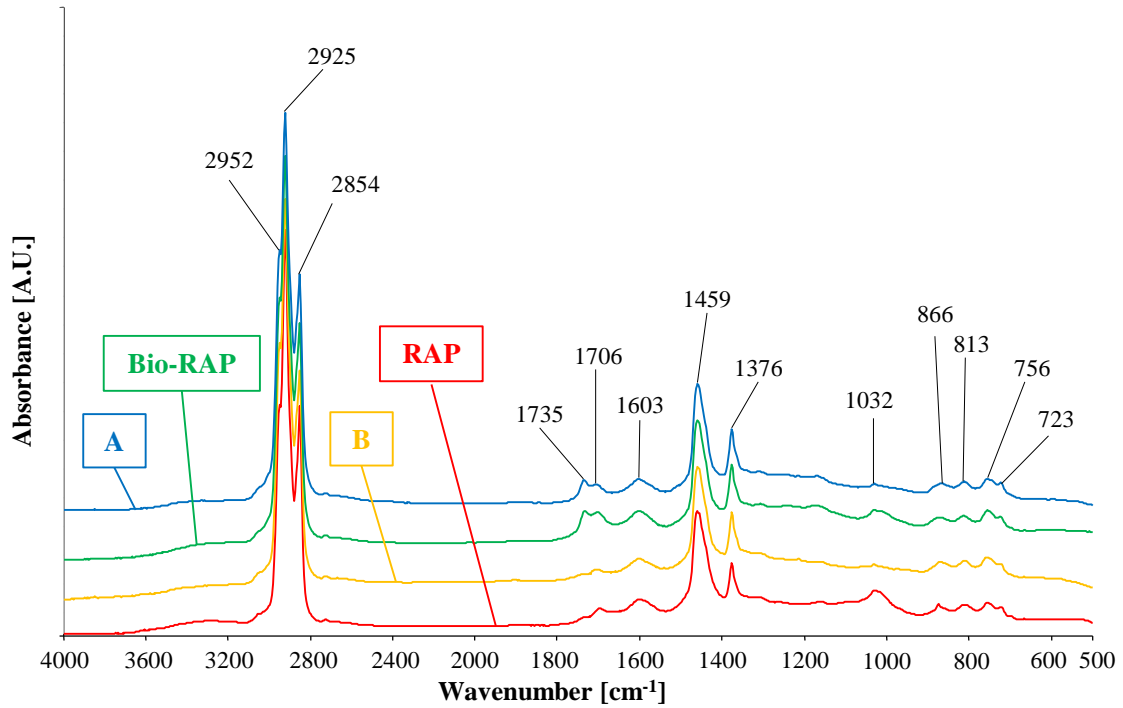


Figure 9 – FTIR spectra of the base binders

No additional peaks were observed in the spectra of the recycled blends, indicating that in all cases only a physical blending occurred between the binders, without any chemical reaction (not even in the presence of the bio-binder). Therefore, in the quantitative analysis, the area between 1679 and 1753 cm^{-1} (A_{CO}) and the area between 972 and 1063 cm^{-1} (A_{SO}) were calculated. It should be pointed out that both peaks at 1700 and 1735 cm^{-1} were included in the calculation of A_{CO} because of the peculiar shape of the bio-binder spectrum in this wavenumber range (see Figure 9), which does not allow to consider these peaks as completely distinct and independent from each other. In order to minimise the influence of specimen thickness (or infrared radiation path length), these areas were normalised as in Equations (5) and (6), where A_{ref} is the reference area between 1330 and 1518 cm^{-1} including the peaks at 1376 and 1459 cm^{-1} , which correspond to the CH_3 and CH_2 bend of the aliphatic groups (that are supposed not to be affected by oxidation) (Marsac et al., 2014).

$$I_{CO} = \frac{A_{CO}}{A_{ref}} \quad (5)$$

$$I_{SO} = \frac{A_{SO}}{A_{ref}} \quad (6)$$

429 The indices I_{CO} and I_{SO} calculated for the recycled blends and the Control bitumen are shown in
430 Figures 10a and 10b, respectively, whereas their sum is shown in Figure 10c. It should be noted
431 that, in Figure 10, each graph presents a different scale on the y-axis to emphasize the differences
432 between the binders.

433 As can be seen from Figure 10a, the index I_{CO} increases with aging for all binders, and such
434 increment seems to be almost linear. Moreover, it can be noted that the blends containing the bio-oil
435 exhibit higher I_{CO} values due to the peak at 1735 cm^{-1} . Indeed, the highest values are shown by
436 A+bio-RAP, followed by A+RAP and B+bio-RAP, whereas B+RAP and the Control bitumen
437 exhibit significantly lower I_{CO} values.

438 Conversely, the index I_{SO} is almost unchanged after RTFOT, while it markedly increases after long-
439 term aging (PAV) (Figure 10b). In general, higher I_{SO} values are observed in the presence of RAP
440 (A+RAP and B+RAP), as this binder was recovered from the reclaimed asphalt deriving from a
441 pavement which was in service for more than 20 years (see Section 2.1). Furthermore, since the
442 Control bitumen is entirely virgin (unlike the recycled blends), it exhibits the lowest I_{SO} values,
443 especially in unaged and short-term aged conditions.

444 Finally, the sum of I_{CO} and I_{SO} seems to be a reliable chemical aging indicator, as it increases with
445 aging for all binders (Figure 10c). Specifically, this increment is relatively small after RTFOT,
446 whereas it becomes larger after PAV, which seems consistent with the severity of the mechanical
447 changes typically undergone by bituminous binders after short-term and long-term aging. A similar
448 FTIR index was effectively used in a previous study to compare the aging susceptibility of this type
449 of bio-binders and conventional bitumens (Ingrassia et al., 2019b).

450

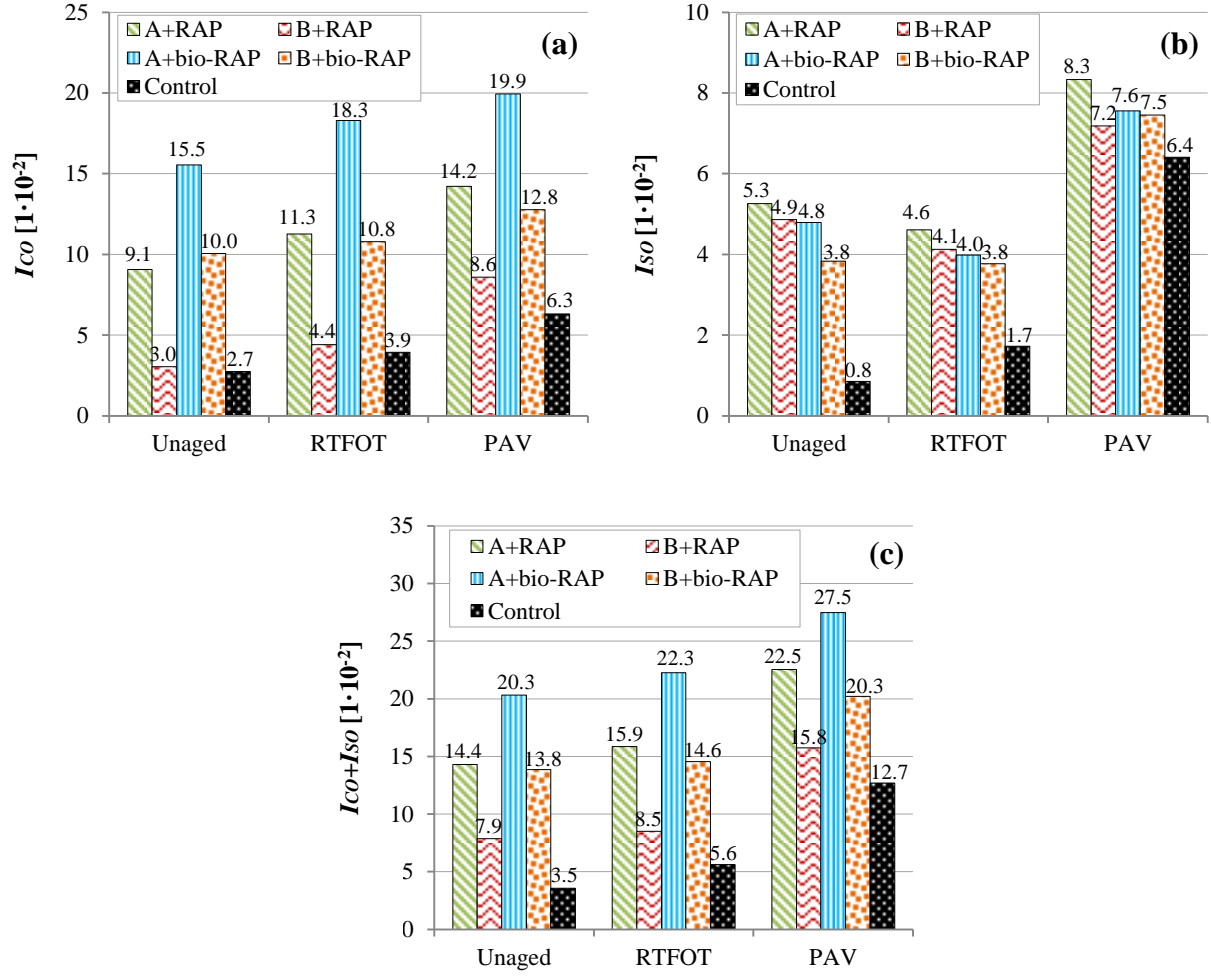


Figure 10 – FTIR indices: (a) I_{CO} , (b) I_{SO} , (c) $I_{CO} + I_{SO}$

3.6 Aging susceptibility

In order to compare the aging susceptibility of the binders, one chemical and one mechanical parameter strictly related to the oxidation of the binders were considered.

From the chemical point of view, it is generally known that the FTIR spectrum is a sort of chemical fingerprint of the material (Smith, 2011). In Section 3.5, it has been shown that, for the binders studied, aging causes the formation of additional compounds at 1700, 1735 and 1030 cm^{-1} , quantified through the sum of the indices I_{CO} and I_{SO} .

Therefore, the chemical aging index AI_{FTIR} , defined as the ratio between $I_{CO} + I_{SO}$ for the aged binder and $I_{CO} + I_{SO}$ for the unaged binder (Equation (7)), was considered.

$$AI_{FTIR} = \frac{(I_{CO} + I_{SO})_{aged}}{(I_{CO} + I_{SO})_{unaged}} \quad (7)$$

466 From the mechanical standpoint, instead, different parameters are considered in literature to study
 467 the aging susceptibility of bituminous binders. Some of them are based on the results of
 468 conventional test (e.g. the retained penetration and the softening point increment), while others are
 469 more performance-based (i.e. calculated from the results of rheological testing and/or modelling). In
 470 general, a reliable mechanical aging index should be unambiguously related to the evolution of the
 471 binder oxidation. In Sections 3.2, 3.3 and 3.4, it has been shown that the modified CAM parameters
 472 m_e and R and the WLF parameters C_1 and C_2 exhibit a clear trend with aging, but their variation due
 473 to aging is relatively small as compared to that of the fatigue parameter $|G^*|\sin\delta$, the non-
 474 recoverable creep compliance J_{nr} and the percent strain recovery $\%R$. Moreover, it is worth pointing
 475 out that $|G^*|\sin\delta$, J_{nr} and $\%R$ are determined directly from rheological tests, whereas the modified
 476 CAM and WLF parameters are the results of a modelling procedure that might be affected by a
 477 certain degree of inaccuracy. In addition, the effect of oxidative aging can be more easily quantified
 478 at very low frequencies/very high temperatures (Rad et al., 2018). Therefore, based on these
 479 considerations, J_{nr} was considered as the most appropriate mechanical parameter to be used in the
 480 analysis of the aging susceptibility of the binders studied. Specifically, the values of J_{nr} determined
 481 at the highest stress level (3.2 kPa) and 70 °C were considered. This temperature was chosen among
 482 those investigated (60, 70 and 80 °C) because the recycled blends and the Control bitumen should
 483 have an upper performance grade (PG) close to 70 °C.
 484 Since the non-recoverable creep compliance decreases with aging, the mechanical aging index
 485 AI_{MSCR} was defined as the ratio between J_{nr} of the unaged binder and J_{nr} of the aged binder
 486 (Equation (8)), in order to have AI values higher than 1 (as in the case of AI_{FTIR}).

$$AI_{MSCR} = \frac{(J_{nr}@70^\circ C, 3.2 \text{ kPa})_{unaged}}{(J_{nr}@70^\circ C, 3.2 \text{ kPa})_{aged}} \quad (8)$$

488
 489 The values of AI_{FTIR} and AI_{MSCR} obtained are shown in Figures 11a and 11b, respectively. Firstly, it
 490 can be observed that, after short-term aging, no big differences emerge between the binders (except
 491 for AI_{FTIR} for the Control bitumen), probably because this aging condition is not severe enough to
 492 assess the aging susceptibility of the binders or all the studied binders are highly aging-resistant in
 493 RTFOT. On the contrary, after long-term aging, there is a clear distinction between the binders,
 494 which are ranked as follows (from the highest to the lowest aging susceptibility): Control bitumen,
 495 B+RAP, A+RAP, B+bio-RAP, A+bio-RAP. It should be noted that this ranking is observed both in
 496 terms of AI_{FTIR} and AI_{MSCR} after PAV.

497 These findings indicate that the aging susceptibility of the recycled blends is significantly lower
 498 than that of the Control bitumen, analogously to previous results by Mazzoni et al. (2018). As a
 499 possible explanation of this phenomenon, it should be considered that the recycled blends already
 500 contain a certain amount of severely aged binder, and the aging rate tends to be faster when the
 501 binder is virgin while it progressively slows down as aging develops (Luo et al., 2018). Moreover,
 502 the blends containing Bio-RAP as aged binder (A+bio-RAP and B+bio-RAP) have lower aging
 503 susceptibility than the blends containing RAP (A+RAP and B+RAP). At the same time, the blends
 504 containing the bio-binder A as fresh binder (A+RAP and A+bio-RAP) tend to exhibit lower aging
 505 susceptibility than the blends containing the conventional bitumen B (B+RAP, B+bio-RAP). These
 506 results are fully in agreement with previous findings by Ingrassia et al. (2019b), who observed that
 507 this type of bio-binders is less affected by aging as compared to conventional bitumens with similar
 508 penetration grade.
 509

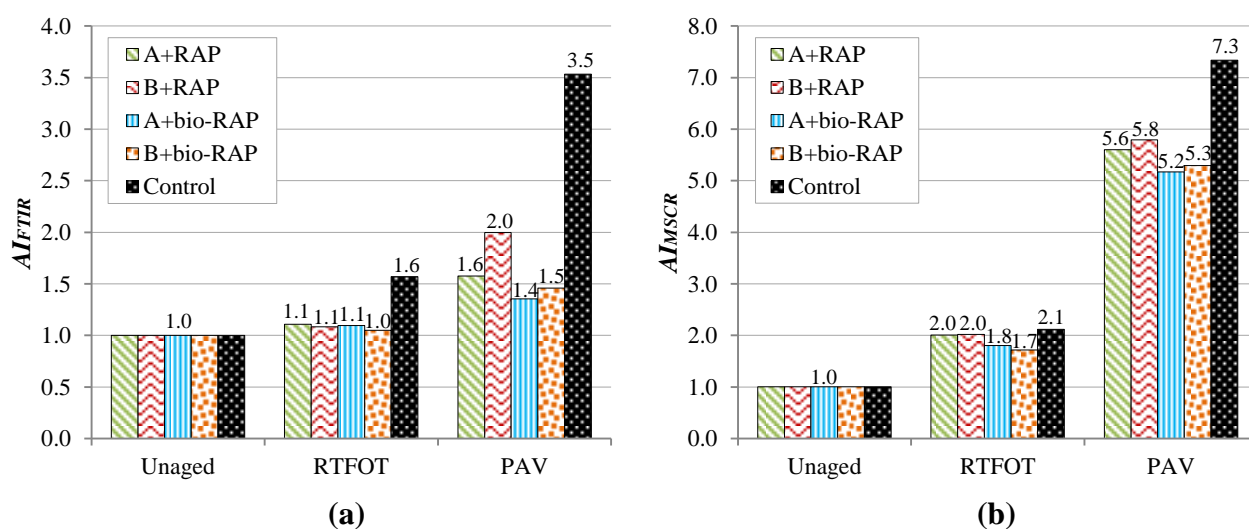


Figure 11 – Aging index based on (a) FTIR results, (b) MSCR results

513 Based on these outcomes and on the results provided in Sections 3.3 and 3.4, the hot recycling of
 514 bio-RA may lead to asphalt mixtures less susceptible to cracking as compared to the recycling of
 515 conventional RA, as well as the use of bio-binders in the hot recycling of conventional RA may be
 516 beneficial in terms of cracking, thanks to a lower aging rate of the binder. On the other hand, the
 517 reduced aging undergone by the blends with the bio-binder might imply a higher rutting tendency
 518 for the resulting asphalt mixture. Nevertheless, it should be emphasized that rutting is usually a
 519 concern when the binder is unaged or short-term aged, and under these circumstances the behaviour
 520 of all the recycled blends studied is broadly the same. Moreover, the results obtained suggest that

521 mixtures containing reclaimed asphalt may be characterized by a lower aging rate as compared to
 522 virgin asphalt mixtures (with possible consequences in terms of mechanical behaviour).
 523 In Figure 12, three pairs of values (AI_{FTIR} , AI_{MSCR}) are plotted for every binder. The pair at (1,1) is
 524 the origin of the graph, as it represents the unaged condition (“zero” condition) for all binders,
 525 intermediate (AI_{FTIR} , AI_{MSCR}) values represent the short-term aged condition, whereas the highest
 526 (AI_{FTIR} , AI_{MSCR}) values correspond to the long-term aged condition. The figure demonstrates that, if
 527 the binders are examined separately, there is an excellent linear relationship between AI_{MSCR} and
 528 AI_{FTIR} (R^2 very close to 1), indicating that the chemical and mechanical parameters considered as
 529 aging indicators (I_{CO+ISO} and J_{nr}) are effectively correlated with the binder oxidation.
 530

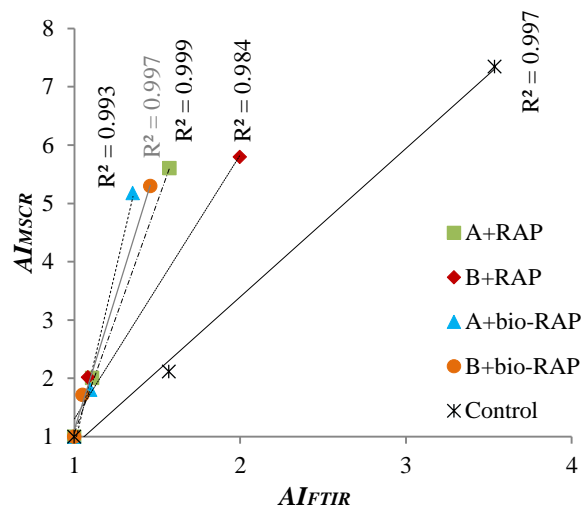


Figure 12 – Correlation between AI_{MSCR} and AI_{FTIR}

531

532

533

534

535 4. Conclusions

536 The objectives of this study were 1) to assess the effectiveness of bio-binders in the hot recycling of
 537 bitumen from typical reclaimed asphalt (RA), and 2) to evaluate the recyclability potential of bio-
 538 binders. Two severely aged binders (one “RAP” binder recovered from reclaimed asphalt and one
 539 laboratory-produced “Bio-RAP” binder) and two fresh binders (one bio-binder and one bitumen)
 540 were properly blended to simulate four binders resulting from the hot recycling of asphalt. The
 541 blends were then short-term and long-term aged in order to investigate their aging susceptibility.
 542 The mechanical behaviour and the aging susceptibility of the recycled blends were also compared to
 543 those of a common virgin bitumen (Control). The experimental investigation included mechanical
 544 tests (conventional tests as well as rheological testing and modelling) and chemical analysis
 545 (Fourier transform infrared spectroscopy).

The main conclusions can be summarized as follows:

- FTIR analysis highlights that, for all the binders tested (with and without the bio-binder), oxidative aging can be tracked from the chemical point of view by considering the formation of C=O bonds at 1700 and 1735 cm^{-1} plus S=O bonds at 1030 cm^{-1} .
- From the mechanical point of view, the aging susceptibility of the binders studied can be assessed through the evolution of the non-recoverable creep compliance, which is linearly correlated with the chemical oxidation for each binder.
- The recycled blends containing the bio-binder undergo lower aging than the corresponding blends containing the conventional bitumen.
- The hot recycling of reclaimed bio-asphalt (bio-RA) may lead to mixtures less susceptible to cracking as compared to the recycling of conventional RA, as well as the use of bio-binders in the hot recycling of conventional RA may be beneficial in terms of cracking, thanks to a lower aging rate of the binder.
- The reduced aging undergone by the blends with the bio-binder might imply a higher rutting tendency for the resulting asphalt mixture. However, the behaviour of all the recycled blends studied is generally comparable in unaged and short-term aged conditions, i.e. when rutting is usually a concern.
- The recycled blends show significantly lower aging susceptibility than the Control bitumen (virgin), probably because they already contain a certain percentage of severely aged binder.

Overall, these results suggest that bio-binders can be considered effective in the hot recycling of RA and 100% recyclable, and their use in asphalt pavements can lead to significant technical as well as environmental benefits. However, the results of this investigation should be integrated also with the study of other aspects, such as low-temperature performance and water sensitivity.

Future work will focus on the performance-based characterization of bio-asphalt mixtures and corresponding traditional asphalt mixtures.

Conflict of interest

The authors declare that there is no conflict of interest regarding the publication of this paper.

580 **References**

- 581 Abdullahi Ahmad, K., Ezree Abdullah, M., Abdul Hassan, N., Usman, N., Ambak, K., 2017. Investigating
582 the feasibility of using jatropha curcas oil (JCO) as bio based rejuvenator in reclaimed asphalt pavement
583 (RAP). MATEC Web of Conferences 103, 09013, <https://doi.org/10.1051/matecconf/201710309013>.
- 584 Anderson, D.A., Christensen, D.W., Bahia, H.U., Dongre, R., Sharma, M.G., Antle, C.E., Button, J., 1994.
585 Binder characterization and evaluation, volume 3: physical characterization, SHRP Report A-369, Strategic
586 Highway Research Program, National Research Council, Washington DC.
- 587 Bahia, H.U., Hanson, D.I., Zeng, M., Zhai, H., Khatri, M.A., Anderson, R.M., 2001. Characterization of
588 modified asphalt binders in Superpave mix design. NCHRP Report 459. Transportation Research Board,
589 Washington DC.
- 590 Bearsley, S.R., Haverkamp, R.G., 2007. Adhesive properties of tall oil pitch modified bitumen. Road
591 Materials and Pavement Design, 8 (3), 449-465.
- 592 Behnood, A., 2019. Application of rejuvenators to improve the rheological and mechanical properties of
593 asphalt binders and mixtures: A review. Journal of Cleaner Production, 231, 171-182,
594 <https://doi.org/10.1016/j.jclepro.2019.05.209>.
- 595 Bowers, B.F., Huang, B., Shu, X., 2014. Refining laboratory procedure for artificial RAP: A comparative
596 study. Construction and Building Materials, 52, 385-390,
597 <http://dx.doi.org/10.1016/j.conbuildmat.2013.11.003>.
- 598 Brundtland, G.H., 1987. Our common future – Report of the World Commission on Environment and
599 Development, Oxford University Press, Oxford.
- 600 Cavalli, M.C., Zaumanis, M., Mazza, E., Partl, M.N., Poulikakos, L.D., 2018. Aging effect on rheology and
601 cracking behaviour of reclaimed binder with bio-based rejuvenators. Journal of Cleaner Production, 189, 88-
602 97, <https://doi.org/10.1016/j.jclepro.2018.03.305>.
- 603 EN 12607-1, 2015. Bitumen and bituminous binders – Determination of the resistance to hardening under
604 influence of heat and air – Part 1: RTFOT method.
- 605 EN 12697-3, 2018. Bituminous mixtures – Test methods – Part 3: Bitumen recovery: Rotary evaporator.
- 606 EN 1426, 2015. Bitumen and bituminous binders – Determination of needle penetration.
- 607 EN 1427, 2015. Bitumen and bituminous binders – Determination of the softening point – Ring and Ball
608 method.
- 609 EN 14769, 2013. Bitumen and bituminous binders – Accelerated long-term aging conditioning by a Pressure
610 Ageing Vessel (PAV).

611 EN 14770, 2012. Bitumen and bituminous binders – Determination of complex shear modulus and phase
612 angle – Dynamic Shear Rheometer (DSR).

613 EN 16659, 2015. Bitumen and bituminous binders – Multiple Stress Creep and Recovery Test (MSCRT).

614 Fini, E.H., Kalberer, E.W., Shahbazi, A., Basti, M., You, Z., Ozer, H., Aurangzeb, Q., 2011. Chemical
615 characterization of biobinder from swine manure: Sustainable modifier for asphalt binder. *Journal of*
616 *Materials in Civil Engineering*, 23 (11), 1506-1513, DOI: 10.1061/(ASCE)MT.1943-5533.0000237.

617 Geissdoerfer, M., Savaget, P., Bocken, N.M.P., Hultink, E.J., 2017. The circular economy – a new
618 sustainability paradigm? *Journal of Cleaner Production*, 143, 757-768,
619 <https://doi.org/10.1016/j.jclepro.2016.12.048>.

620 Ghisellini, P., Ji, X., Liu, G., Ulgiati, S., 2018. Evaluating the transition towards cleaner production in
621 the construction and demolition sector of China: A review. *Journal of Cleaner Production*, 195, 418-434,
622 <https://doi.org/10.1016/j.jclepro.2018.05.084>.

623 Gong, M., Yang, J., Zhang, J., Zhu, H., Tong, T., 2016. Physical-chemical properties of aged asphalt
624 rejuvenated by bio-oil derived from biodiesel residue. *Construction and Building Materials*, 105, 35-45,
625 <https://doi.org/10.1016/j.conbuildmat.2015.12.025>.

626 He, M., Tu, C., Cao, D.W., Chen, Y.J., 2019. Comparative analysis of bio-binder properties derived from
627 different sources. *International Journal of Pavement Engineering*, 20 (7), 792-800,
628 <https://doi.org/10.1080/10298436.2017.1347434>.

629 Hendrickson, C., Horvath, A., 2000. Resource use and environmental emissions of U.S. construction sectors.
630 *Journal of Construction Engineering and Management*, 126 (1), 38-44, [https://doi.org/10.1061/\(ASCE\)0733-](https://doi.org/10.1061/(ASCE)0733-9364(2000)126:1(38))
631 [9364\(2000\)126:1\(38\)](https://doi.org/10.1061/(ASCE)0733-9364(2000)126:1(38)).

632 Hofko, B., Alavi, M.Z., Grothe, H., Jones, D., Harvey, J., 2017. Repeatability and sensitivity of FTIR ATR
633 spectral analysis methods for bituminous binders. *Materials and Structures*, 50, 187, DOI: 10.1617/s11527-
634 017-1059-x.

635 Hosseinneshad, S., Zadshir, M., Yu, X., Yin, H., Sharma, B.K., Fini, E.H., 2019. Differential effects of
636 ultraviolet radiation and oxidative aging on bio-modified binders. *Fuel*, 251, 45-56,
637 <https://doi.org/10.1016/j.fuel.2019.04.029>.

638 Ingrassia, L.P., Lu, X., Ferrotti, G., Canestrari, F., 2019a. Renewable materials in bituminous binders and
639 mixtures: Speculative pretext or reliable opportunity? *Resources, Conservation and Recycling*, 144, 209-222,
640 <https://doi.org/10.1016/j.resconrec.2019.01.034>.

641 Ingrassia, L.P., Lu, X., Ferrotti, G., Canestrari, F., 2019b. Chemical and rheological investigation on the
 642 short- and long-term aging properties of bio-binders for road pavements. *Construction and Building*
 643 *Materials*, 217, 518-529, <https://doi.org/10.1016/j.conbuildmat.2019.05.103>.

644 Ingrassia, L.P., Cardone, F., Canestrari, F., Lu, X., 2019c. Experimental investigation on the bond strength
 645 between sustainable road bio-binders and aggregate substrates. *Materials and Structures*, 52, 80,
 646 <https://doi.org/10.1617/s11527-019-1381-6>.

647 Ingrassia, L.P., Lu, X., Ferrotti, G., Canestrari, F., 2019d. Chemical, morphological and rheological
 648 characterization of bitumen partially replaced with wood bio-oil: Towards more sustainable materials in road
 649 pavements. *Journal of Traffic and Transportation Engineering (English Edition)*,
 650 <https://doi.org/10.1016/j.jtte.2019.04.003>.

651 Jiménez del Barco Carrión, A., Lo Presti, D., Pouget, S., Chailleux, E., Airey, G.D., 2017. Toward non-
 652 petroleum-derived asphalt mixes: Using biobinders for high-modulus asphalt mixes with high reclaimed
 653 asphalt content. *Transportation Research Board 96th Annual Meeting*, Washington DC, 8-12 January 2017.

654 Kennedy, T.W., Huber, G.A., Harrigan, E.T., Cominsky, R.J., Hughes, C.S., Von Quintus, H., Moulthrop,
 655 J.S., 1994. Superior performing asphalt pavements (Superpave): the product of the SHRP Asphalt Research
 656 Program, SHRP Report A-410, Strategic Highway Research Program, National Research Council,
 657 Washington DC.

658 Kowalski, K.J., Król, J.B., Bańkowski, W., Radziszewski, P., Sarnowski, M., 2017. Thermal and fatigue
 659 evaluation of asphalt mixtures containing RAP treated with a bio-agent. *Applied Sciences (Switzerland)*, 7
 660 (3), 216, <https://doi.org/10.3390/app7030216>.

661 Kucukvar, M., Tatari, O., 2013. Towards a triple bottom-line sustainability assessment of the U.S.
 662 construction industry. *International Journal of Life Cycle Assessment*, 18 (5), 958-972, DOI:
 663 10.1007/s11367-013-0545-9.

664 Lo Presti, D., Vasconcelos, K., Orešković, M., Pires, G.M., Bressi, S., 2019. On the degree of binder activity
 665 of reclaimed asphalt and degree of blending with recycling agents. *Road Materials and Pavement Design*, in
 666 press, <https://doi.org/10.1080/14680629.2019.1607537>.

667 Lu, D.X., Saleh, M., Nguyen, N.H.T., 2019. Effect of rejuvenator and mixing methods on behaviour of warm
 668 mix asphalt containing high RAP content. *Construction and Building Materials*, 197, 792-802,
 669 <https://doi.org/10.1016/j.conbuildmat.2018.11.205>.

670 Luo, X., Gu, F., Zhang, Y., Lytton, R.L., Birgisson, B., 2018. Kinetics-based aging evaluation of in-service
 671 recycled asphalt pavement. *Journal of Cleaner Production*, 200, 934-944,
 672 <https://doi.org/10.1016/j.jclepro.2018.07.267>.

673 Marsac, P., Piérard, N., Porot, L., Van den bergh, W., Grenfell, J., Mouillet, V., Pouget, S., Besamusca, J.,
674 Farcas, F., Gabet, T., Hugener, M., 2014. Potential and limits of FTIR methods for reclaimed asphalt
675 characterisation. *Materials and Structures*, 47, 1273-1286, DOI: 10.1617/s11527-014-0248-0.

676 Mazzoni, G., Bocci, E., Canestrari, F., 2018. Influence of rejuvenators on bitumen ageing in hot recycled
677 asphalt mixtures. *Journal of Traffic and Transportation Engineering (English Edition)*, 5 (3), 157-168,
678 <https://doi.org/10.1016/j.jtte.2018.01.001>.

679 Petersen, J.C., 2009. A review of the fundamentals of asphalt oxidation. *Transportation Research Circular E-*
680 *C140*.

681 Petersen, J.C., Glaser, R., 2011. Asphalt oxidation mechanisms and the role of oxidation products on age
682 hardening revisited. *Road Materials and Pavement Design*, 12 (4), 795-819,
683 <https://doi.org/10.1080/14680629.2011.9713895>.

684 Rad, F.Y., Elwardany, M.D., Castorena, C., Kim, Y.R., 2018. Evaluation of chemical and rheological aging
685 indices to track oxidative aging of asphalt mixtures. *Transportation Research Record*, 2672 (28), 349-358,
686 <https://doi.org/10.1177/0361198118784138>.

687 Raouf, M.A., Williams, C.R., 2010. General rheological properties of fractionated switchgrass bio-oil as a
688 pavement material. *Road Materials and Pavement Design*, 11 (special issue), 325-353, DOI:
689 10.3166/RMPD.11HS.325-353.

690 Samieadel, A., Schimmel, K., Fini, E.H., 2018a. Comparative life cycle assessment (LCA) of bio-modified
691 binder and conventional asphalt binder. *Clean Technologies and Environmental Policy*, 20 (1), 191-200,
692 <https://doi.org/10.1007/s10098-017-1467-1>.

693 Samieadel, A., Oldham, D.J., Fini, E.H., 2018b. Investigating molecular conformation and packing of
694 oxidized asphaltene molecules in presence of paraffin wax. *Fuel*, 220, 503-512,
695 <https://doi.org/10.1016/j.fuel.2018.02.031>.

696 Shirodkar, P., Mehta, Y., Nolan, A., Sonpal, K., Norton, A., Tomlinson, C., Dubois, E., Sullivan, P. Sauber,
697 R., 2011. A study to determine the degree of partial blending of reclaimed asphalt pavement (RAP) binder
698 for high RAP hot mix asphalt. *Construction and Building Materials*, 25, 150-155,
699 <https://doi.org/10.1016/j.conbuildmat.2010.06.045>.

700 Smith, B.C., 2011. *Fundamentals of Fourier Transform Infrared Spectroscopy*. CRC Press, Boca Raton FL.

701 Stimilli, A., Virgili, A., Canestrari, F., 2015. New method to estimate the “re-activated” binder amount in
702 recycled hot-mix asphalt. *Road Materials and Pavement Design*, 16, 442-459,
703 <http://dx.doi.org/10.1080/14680629.2015.1029678>.

704 Sun, Z., Yi, J., Huang, Y., Feng, D., Guo, C., 2016. Properties of asphalt binder modified by bio-oil derived
705 from waste cooking oil. *Construction and Building Materials*, 102, 496-504,
706 <https://doi.org/10.1016/j.conbuildmat.2015.10.173>.

707 Williams, M.L., Landel, R.F., Ferry, J.D., 1955. The temperature dependence of relaxation mechanisms in
708 amorphous polymers and other glass-forming liquids. *Journal of the American Chemical Society*, 77 (14),
709 3701-3707, DOI: 10.1021/ja01619a008.

710 Yang, X., You, Z., Dai, Q., Mills-Beale, J., 2014. Mechanical performance of asphalt mixtures modified by
711 bio-oils derived from waste wood resources. *Construction and Building Materials*, 51, 424-431,
712 <https://doi.org/10.1016/j.conbuildmat.2013.11.017>.

713 Yusoff, N.I.M., Shaw, M.T., Airey, G.D., 2011. Modelling the linear viscoelastic rheological properties of
714 bituminous binders. *Construction and Building Materials*, 25 (5), 2171-2189,
715 <https://doi.org/10.1016/j.conbuildmat.2010.11.086>.

716 Zadshir, M., Oldham, D.J., Hosseinneshad, S., Fini, E.H., 2018. Investigating bio-rejuvenation mechanisms
717 in asphalt binder via laboratory experiments and molecular dynamics simulation. *Construction and Building*
718 *Materials*, 190, 392-402, <https://doi.org/10.1016/j.conbuildmat.2018.09.137>.

719 Zaumanis, M., Boesiger, L., Kunz, B., Cavalli, M.C., Poulikakos, L., 2019. Determining optimum
720 rejuvenator addition location in asphalt production plant. *Construction and Building Materials*, 198, 368-378,
721 <https://doi.org/10.1016/j.conbuildmat.2018.11.239>.

722 Zaumanis, M., Mallick, R.B., 2015. Review of very high-content reclaimed asphalt use in plant-produced
723 pavements: State of the art. *International Journal of Pavement Engineering*, 16 (1), 39-55,
724 <https://doi.org/10.1080/10298436.2014.893331>.

725 Zaumanis, M., Mallick, R.B., Frank, R., 2014a. 100% recycled hot mix asphalt: A review and analysis.
726 *Resources, Conservation and Recycling*, 92, 230-245, <https://doi.org/10.1016/j.resconrec.2014.07.007>.

727 Zaumanis, M., Mallick, R.B., Poulikakos, L., Frank, R., 2014b. Influence of six rejuvenators on the
728 performance properties of reclaimed asphalt pavement (RAP) binder and 100% recycled asphalt mixtures.
729 *Construction and Building Materials*, 71, 538-550, <https://doi.org/10.1016/j.conbuildmat.2014.08.073>.